

KERAKOLL SpA Headquarter
via Pedemontana, 25
41049 Sassuolo (MO)
Italy

Test Report No. 59465-A013-AgBB-L

| | |
|---|--|
| Test objective: | Evaluation according to AgBB scheme 2021 |
| Article designation according to order: | BIOCALCE FONDO |
| Date of report: | 31/01/2025 |
| Number of pages of report: | 20 |
| Testing / responsible laboratory: | eco-INSTITUT Germany GmbH, Köln |
| Test objective fulfilled: | ✓ |

Note:

The test results in the report refer exclusively to the test sample submitted by the manufacturer. The report is not permitted to be used in product and company advertising. The report may be published in full as technical documentation on the Internet with the written consent of eco-INSTITUT Germany GmbH. eco-INSTITUT Germany GmbH has recommended that the manufacturer repeats the test after 3 years at the latest. More information at www.eco-institut.de/en/advertising

Content

| | |
|---|----|
| Sample View | 3 |
| Statement of conformity with AgBB 2021 | 4 |
| Summary statement of conformity with AgBB 2021 | 5 |
| Laboratory report..... | 6 |
| 1 Emission analysis..... | 6 |
| 1.1 Sample A013, Volatile organic compounds after 3 days..... | 7 |
| 1.2 Sample A013, Volatile organic compounds after 28 days | 11 |
| Appendix..... | 14 |
| Sampling sheet..... | 14 |
| List of calibrated Volatile Organic Compounds (VOC)..... | 15 |
| Definition of terms..... | 17 |
| Commentary on emission analysis..... | 19 |
| Explanation of Specific Emission Rate SER | 20 |


‡ subcontracted, # outside accreditation

Sample View

Internal sample number (filled in by laboratory)

59465-A013

Photo of the test specimen: A013

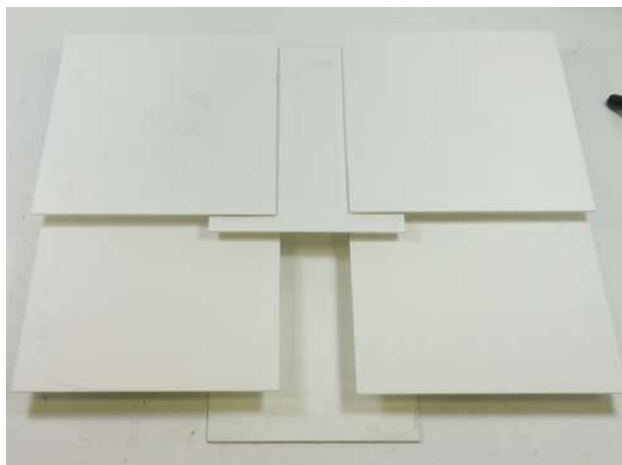

Article designation according to order:

BIOCALCE FONDO

Sample/batch number according to order:

PTKK00176

Type of sample:

PTKK00176

Date of production:

5241002032 21.03.2024

Sampling by:

Marina Bastarolo

Date of sampling:

17/07/2024

Location of sampling:

no information

Receipt of sample / Condition upon delivery:

06/09/2024 / without objection

Statement of conformity with AgBB 2021

The sample with the internal sample number 59465-A013 has been tested on behalf of **KERAKOLL SpA Headquarter**. The article description according to the order is **BIOCALCE FONDO**.

This evaluation is based on the test criteria of the scheme “Health-related Evaluation of Emissions of Volatile Organic Compounds (VVOC, VOC and SVOC) from Building Products” of the Committee for Health-Related Evaluation of Building Products (AgBB 2021).

The results documented in the test report were evaluated as follows.¹

| Test parameter | Result | Requirement | Requirement hold [yes/no] |
|--|---------------------------|---------------------------|---------------------------|
| Emission analysis | | | |
| Measurement time: 3 days after test chamber loading | | | |
| Sum VOC (C6-C16) ¹⁾ | 4.3 mg/m ³ | ≤ 10 mg/m ³ | yes |
| Carcinogenic substances, cat. 1A and 1B acc. to Regulation (EC) No. 1272/2008 (and TRGS 905) (per substance) | ≤ 0.01 mg/m ³ | ≤ 0.01 mg/m ³ | yes |
| Measurement time: 28 days after test chamber loading | | | |
| Sum VOC (C6-C16) including SVOC with LCI ¹⁾ | 0.69 mg/m ³ | ≤ 1.0 mg/m ³ | yes |
| Sum SVOC without LCI (C16-C22) ¹⁾ | < 0.005 mg/m ³ | ≤ 0.1 mg/m ³ | yes |
| R-value (dimensionless) | 0.12 | ≤ 1 | yes |
| Sum VOC without LCI | < 0.005 mg/m ³ | ≤ 0.1 mg/m ³ | yes |
| Carcinogenic substances, cat. 1A and 1B acc. to Regulation (EC) No. 1272/2008 (and TRGS 905) (per substance) | ≤ 0.001 mg/m ³ | ≤ 0.001 mg/m ³ | yes |

1) For sum VOC (C6-C16) and sum SVOC (C16-C22) only substances ≥ 5 µg/m³ are considered.

¹ If a measurement result that slightly exceeds the specification is assessed as “not fulfilled”, this is based on the agreement of the “shared risk of measurement uncertainty (shared risk approach)”. According to this, the probability that the statement is correct is ≥ 50 %. Similarly, a result slightly below the specification value also only has a probability of ≥ 50 % of being compliant. I.e., the risk of making a false negative statement regarding the fulfilment of the specification is just as high as the risk of making a false positive statement (more information at https://www.eco-institut.de/en/2019/07/measurement_uncertainty/).

Summary statement of conformity with AgBB 2021

The sample with the internal sample number 59465-A013, article description according to order: **BIOCALCE FONDO**, meets the emission requirements of the AgBB scheme.

Cologne, 31/01/2025

A handwritten signature in black ink, appearing to read "M.A. Dobaj".

Marc-Anton Dobaj, M.Sc. Crystalline Materials
(Project management)

Laboratory report

1 Emission analysis

Test method

DIN EN 16516:2020-10

Testing and evaluation of the release of dangerous substances;
determination of emissions into indoor air

A013, Preparation of test specimen

Date:

26/11/2024

Test specimen preparation:

Application on glass; with a brush; application quantity 370 g/m²;
drying / pre-conditioning outside of the test chamber for 72 hours

Masking of backside:

not applicable

Masking of edges:

not applicable

Relationship of unmasked
edges to surface:

not applicable

Arrangement in test chamber:

on tripod

Loading reference unit:

area-specific [m²]

Dimensions:

4 x 25.0 cm x 25.0 cm with each 23.1 g application + 2 x 25.0 cm x 20.0 cm
with 18.5 g application

A013, Test chamber conditions according to DIN EN ISO 16000-9:2024-08

Chamber volume:

0.250 m³

Temperature:

23 °C ± 1 °C

Relative humidity:

50 % ± 1 %

Air pressure:

normal

Air:

cleaned

Air change rate:

0.5 h⁻¹

Air velocity:

0.3 m/s

Loading:

1.4 m²/m³

Specific air flow rate:

0.357 m³/(m²·h)

Starting time of the test (t₀):

29/11/2024

Air sampling:

3 days after test chamber loading
28 days after test chamber loading

Analytics

Aldehydes and ketones:

DIN ISO 16000-3:2023-12

Limit of quantification:

2 µg/m³

Volatile organic compounds:

DIN ISO 16000-6:2022-03

Limit of quantification:

1 µg/m³ (1,4-Cyclohexanedimethanol, Diethylene glycol,
1,4-Butanediol: 5 µg/m³)

Note for analysis:

not specified

1.1 Sample A013, Volatile organic compounds after 3 days

Test objective:

Volatile organic compounds (VOC), test chamber, air sampling 3 days after test chamber loading

Test result:

Internal sample number: | 59465-A013

| | Substance | CAS No. | RT [min] | Concentration+ calib. substances ≥ 1 µg/m³ uncalib. substances ≥ 1 µg/m³ DNPH ≥ 2 µg/m³ [µg/m³] | Toluene- equivalent substances ≥ 5 µg/m³ [µg/m³] | SER+ [µg/(m²·h)] | CMR Classifi- cation++ | LCI AgBB 2021 [µg/m³] | R-value |
|------|--|------------|-------------|---|--|---------------------|------------------------------|-----------------------------|---------|
| | Terpenes | | | | | | | | |
| VOC | Longifolene | 475-20-7 | 23.4 | 8 | 5 | 2.9 | | 1400 | 0.01 |
| VOC | Longipinene | 5989-08-2 | 22.14 | 9 | < 5 | 3.2 | | 1400 | 0.01 |
| | Aliphatic mono alcohols (n-, iso-, cyclo-) and dialcohols | | | | | | | | |
| VOC | 2-Ethyl-1-hexanol | 104-76-7 | 14.00 | 5 | 5 | 1.8 | | 300 | 0.02 |
| | Glycols, Glycol ethers, Glycol esters | | | | | | | | |
| VOC | Ethylene glycol (Ethane-1,2-diol) | 107-21-1 | 6.28 | 4 | < 5 | 1.4 | | 3400 | 0.00 |
| VOC | Diethylene glycol | 111-46-6 | 12.35 | 4200 ² | 980 ² | 1500 ² | | 5700 | 0.74 |
| | Aldehydes | | | | | | | | |
| VOC | Hexanal | 66-25-1 | 8.78 | 12 | 5 | 4.3 | | 900 | 0.01 |
| VOC | Heptanal | 111-71-7 | 11.14 | 1 | < 5 | 0.36 | | 900 | 0.00 |
| VOC | Nonanal | 124-19-6 | 15.70 | 13 | 13 | 4.6 | | 900 | 0.01 |
| VOC | 2-Nonenal | 18829-56-6 | 16.91 | 1 | < 5 | 0.36 | | 20 | 0.05 |
| VVOC | Formaldehyde | 50-00-0 | | 2 | n. d. | 0.71 | Carc. 1B Muta. 2 | 100 | 0.02 |
| | Acids | | | | | | | | |
| VOC | Acetic acid | 64-19-7 | 4.37 | 2 | < 5 | 0.71 | | 1200 | 0.00 |

² Detector saturation, the value for concentration can be higher

| | Substance | CAS No. | RT [min] | Concentration+ calib. substances ≥ 1 µg/m³ uncalib. substances ≥ 1 µg/m³ DNPH ≥ 2 µg/m³ [µg/m³] | Toluene- equivalent substances ≥ 5 µg/m³ [µg/m³] | SER+ [µg/(m²·h)] | CMR Classifi- cation++ | LCI AgBB 2021 [µg/m³] | R-value |
|-----|--|----------|-------------|---|--|---------------------|------------------------------|-----------------------------|---------|
| | Other identified substances in addition to LCI list | | | | | | | | |
| VOC | Hexamethylcyclotrisiloxane (D3) | 541-05-9 | 8.83 | 1 | < 5 | 0.36 | | | |
| VOC | Siloxane m/z 105 75 59* | | 5.52 | 2 | < 5 | 0.71 | | | |
| VOC | m/z 91 61 45* | | 5.82 | 8 | 8 | 2.9 | | | |
| VOC | m/z 103 147 117* | | 13.35 | 4 | < 5 | 1.4 | | | |
| VOC | Other terpenes* | -- | 17.69 | 4 | < 5 | 1.4 | | 1400 | 0.00 |
| VOC | m/z 109 91 134* | | 17.85 | 5 | 5 | 1.8 | | | |
| VOC | Other terpenes* | -- | 18.00 | 24 | 24 | 8.6 | | 1400 | 0.02 |
| VOC | Other terpenes* | -- | 18.51 | 3 | < 5 | 1.1 | | 1400 | 0.00 |
| VOC | m/z 103 131 77* | | 21.89 | 1 | < 5 | 0.36 | | | |
| VOC | m/z 73 101 57* | | 23.36 | 2 | < 5 | 0.71 | | | |

+ identified and calibrated substances, substance specific calculated

++ classification according to Regulation (EG) N° 1272/2008: Categories Carc. 1A, 1B and 2, Muta. 1A, 1B and 2, Repr. 1A, 1B and 2, TRGS 905: K1A, K1B, K2, M1A, M1B, M2, R1A, R1B, R2; IARC: Group 1, 2A, 2B and 3, DFG MAK-list: Kategorie III1 to III5

* unidentified substances, calculated as toluene equivalent reported with significant mass fragments as mass-to-charge ratio (m/z)

n. d.: not determined

| Carcinogenic, mutagenic, and reproductive toxic compounds* | Concentration after 3 days [µg/m³] | SERa [µg/(m² · h)] |
|---|------------------------------------|--------------------|
| CMR 1: VOC (incl. VVOC and SVOC) with the following categorisations: Regulation (EC) No. 1272/2008: Category Carc. 1A and 1B, Muta. 1A and 1B, Repr. 1A and 1B; TRGS 905: K1A, K1B, M1A, M1B, R1A, R1B; IARC: Group 1 and 2A; DFG (MAK list): Categories III1, III2 (sum) | < 1 | < 0.36 |
| C 1: VOC (incl. VVOC and SVOC) with the following categorisations: Regulation (EG) Nr. 1272/2008: Category Carc. 1A u. 1B; TRGS 905: K1A, K1B (sum) | < 1 | < 0.36 |

| TVOC, Total volatile organic compounds | Concentration after 3 days [µg/m³] | SERa [µg/(m² · h)] |
|--|------------------------------------|--------------------|
| Sum of VOC according to DIN EN 16516 | 1000 | 370 |
| Sum of VOC according to AgBB 2021 | 4300 | 1500 |
| Sum of VOC according to eco-INSTITUT-Label | 4300 | 1500 |
| Sum of VOC according to DIN ISO 16000-6 | 1100 | 390 |

| TSVOC, Total semi volatile organic compounds | Concentration after 3 days [µg/m³] | SERa [µg/(m² · h)] |
|---|------------------------------------|--------------------|
| Sum of SVOC according to DIN EN 16516 | < 5 | < 1.8 |
| Sum of SVOC without LCI according to AgBB 2021 | < 5 | < 1.8 |
| Sum of SVOC without LCI according to eco-INSTITUT-Label | < 1 | < 0.36 |
| Sum of SVOC with LCI according to AgBB 2021 | < 5 | < 1.8 |

| TVVOC, Total very volatile organic compounds | Concentration after 3 days [µg/m³] | SERa [µg/(m² · h)] |
|--|------------------------------------|--------------------|
| Sum of VVOC according to AgBB 2021 | < 5 | < 1.8 |
| Sum of VVOC according to eco-INSTITUT-Label | 2 | 0.71 |

*Excluding formaldehyde and acetaldehyde (Carc. 1B) due to an assumed "practical threshold" under which a significant carcinogenic risk is no longer to be expected (see Federal Institute for Risk Assessment (2006): Toxicological evaluation of formaldehyde and Federal Environment Agency (2016): Reference value for formaldehyde in indoor air and protocol of the 11th meeting of 'Ausschusses für Innenraumrichtwerte' (AIR), 11/2020). In the case of a toxicological emission assessment, a single-substance analysis of the concentrations is necessary.

In the opinion of the committee for Indoor Air Guide Values (Ausschuss für Innenraumrichtwerte) of the Federal Environment Agency, the concentration of 0.1 mg formaldehyde/m³ indoor air, based on a measurement period of half an hour, should not be exceeded, also for a short time (Bundesgesundheitsblatt 2016 · 59: 1040-1044 DOI 10.1007 / s00103 -016-2389-5 © Springer-Verlag Berlin Heidelberg 2016).

| Other sums of VOC | Concentration after 3 days [µg/m³] | SERa [µg/(m² · h)] |
|--|--|-----------------------|
| VOC without LCI according to AgBB 2021 (sum) | 13 | 4.6 |
| VOC without LCI according to eco-INSTITUT-Label (sum) | 23 | 8.2 |
| CMR 2: VOC (incl. VVOC and SVOC) with the following categorisations: Regulation (EC) No. 1272/2008: Category Carc. 2, Muta. 2, Repr. 2; TRGS 905: K2, M2, R2; IARC: Group 2B; DFG (MAK list): Category III3 (sum) | 2 | 0.71 |
| Sensitising compounds with the following categorisations: DFG (MAK list): Category IV; Regulation (EC) No. 1272/2008: skin sensitising, respiratory sensitising; TRGS 907 (sum) | 10 | 3.6 |
| Bicyclic Terpenes (sum) | < 1 | < 0.36 |
| C9 - C14 Alkanes / Isoalkanes as dekane-equivalent (sum) | < 1 | < 0.36 |
| C4 - C11 Aldehydes, acyclic, aliphatic (sum) | 27 | 9.6 |
| C9 - C15 Alkylated benzenes (sum) | < 1 | < 0.36 |
| Cresols (sum) | < 1 | < 0.36 |

| Risk value for assessment of LCI | R-value |
|---|---------|
| R-value according to eco-INSTITUT-Label | 0.89 |
| R-value according to AgBB 2021 | 0.81 |
| R-value according to Belgian regulation | 0.81 |
| R-value according to EU-LCI | 0.82 |

Note:

Due to different requirements in the respective guidelines, the calculation of TVOC, TVVOC, TSVOC and R-value may result in different values. Short-chain carbonyl compounds (C1-C5) are quantified via HPLC acc. to DIN ISO 16000-3:2013-01. Therefore, no toluene equivalents are given for VVOC. These substances are taken into concern by means of their substance specific calibration via the sum of VVOC acc. to DIN EN 16516:2020-10. For VOC however, the substance specific calibration takes place via HPLC whereas the TVOC is calculated using the toluene equivalent determined via Tenax acc. to DIN EN 16516:2020-10.

1.2 Sample A013, Volatile organic compounds after 28 days

Test objective:

Volatile organic compounds (VOC), test chamber, air sampling 28 days after test chamber loading

Test result:

Internal sample number: | 59465-A013

| | Substance | CAS No. | RT [min] | Concentration+ calib. substances ≥ 1 µg/m³ uncalib. substances ≥ 1 µg/m³ DNPH ≥ 2 µg/m³ [µg/m³] | Toluene- equivalent substances ≥ 5 µg/m³ [µg/m³] | SER+ [µg/(m²·h)] | CMR Classifi- cation++ | LCI AgBB 2021 [µg/m³] | R-value |
|-----|--|----------|-------------|---|--|---------------------|------------------------------|-----------------------------|---------|
| | Aliphatic mono alcohols (n-, iso-, cyclo-) and dialcohols | | | | | | | | |
| VOC | 2-Ethyl-1-hexanol | 104-76-7 | 13.96 | 1 | < 5 | 0.36 | | 300 | 0.00 |
| | Glycols, Glycol ethers, Glycol esters | | | | | | | | |
| VOC | Diethylene glycol | 111-46-6 | 12.46 | 690 | 180 | 250 | | 5700 | 0.12 |
| | Acids | | | | | | | | |
| VOC | Acetic acid | 64-19-7 | 4.34 | 4 | < 5 | 1.4 | | 1200 | 0.00 |
| | Other identified substances in addition to LCI list | | | | | | | | |
| VOC | m/z 91 61 45* | | 5.82 | 3 | < 5 | 1.1 | | | |

+ identified and calibrated substances, substance specific calculated

++ classification according to Regulation (EG) N° 1272/2008: Categories Carc. 1A, 1B and 2, Muta. 1A, 1B and 2, Repr. 1A, 1B and 2, TRGS 905: K1A, K1B, K2, M1A, M1B, M2, R1A, R1B, R2; IARC: Group 1, 2A, 2B and 3, DFG MAK-list: Kategorie III1 to III5

* unidentified substances, calculated as toluene equivalent reported with significant mass fragments as mass-to-charge ratio (m/z)

n. d.: not determined

| Carcinogenic, mutagenic, and reproductive toxic compounds* | Concentration after 28 days [µg/m³] | SERa [µg/(m² · h)] |
|---|-------------------------------------|--------------------|
| CMR 1: VOC (incl. VVOC and SVOC) with the following categorisations: Regulation (EC) No. 1272/2008: Category Carc. 1A and 1B, Muta. 1A and 1B, Repr. 1A and 1B; TRGS 905: K1A, K1B, M1A, M1B, R1A, R1B; IARC: Group 1 and 2A; DFG (MAK list): Categories III1, III2 (sum) | < 1 | < 0.36 |
| C 1: VOC (incl. VVOC and SVOC) with the following categorisations: Regulation (EG) Nr. 1272/2008: Category Carc. 1A u. 1B; TRGS 905: K1A, K1B (sum) | < 1 | < 0.36 |

| TVOC, Total volatile organic compounds | Concentration after 28 days [µg/m³] | SERa [µg/(m² · h)] |
|--|-------------------------------------|--------------------|
| Sum of VOC according to DIN EN 16516 | 180 | 64 |
| Sum of VOC according to AgBB 2021 | 690 | 250 |
| Sum of VOC according to eco-INSTITUT-Label | 700 | 250 |
| Sum of VOC according to DIN ISO 16000-6 | 230 | 82 |

| TSVOC, Total semi volatile organic compounds | Concentration after 28 days [µg/m³] | SERa [µg/(m² · h)] |
|---|-------------------------------------|--------------------|
| Sum of SVOC according to DIN EN 16516 | < 5 | < 1.8 |
| Sum of SVOC without LCI according to AgBB 2021 | < 5 | < 1.8 |
| Sum of SVOC without LCI according to eco-INSTITUT-Label | < 1 | < 0.36 |
| Sum of SVOC with LCI according to AgBB 2021 | < 5 | < 1.8 |

| TVVOC, Total very volatile organic compounds | Concentration after 28 days [µg/m³] | SERa [µg/(m² · h)] |
|--|-------------------------------------|--------------------|
| Sum of VVOC according to AgBB 2021 | < 5 | < 1.8 |
| Sum of VVOC according to eco-INSTITUT-Label | < 1 | < 0.36 |

*Excluding formaldehyde and acetaldehyde (Carc. 1B) due to an assumed "practical threshold" under which a significant carcinogenic risk is no longer to be expected (see Federal Institute for Risk Assessment (2006): Toxicological evaluation of formaldehyde and Federal Environment Agency (2016): Reference value for formaldehyde in indoor air and protocol of the 11th meeting of 'Ausschusses für Innenraumrichtwerte' (AIR), 11/2020). In the case of a toxicological emission assessment, a single-substance analysis of the concentrations is necessary.

In the opinion of the committee for Indoor Air Guide Values (Ausschuss für Innenraumrichtwerte) of the Federal Environment Agency, the concentration of 0.1 mg formaldehyde/m³ indoor air, based on a measurement period of half an hour, should not be exceeded, also for a short time (Bundesgesundheitsblatt 2016 · 59: 1040-1044 DOI 10.1007 / s00103 -016-2389-5 © Springer-Verlag Berlin Heidelberg 2016).

| Other sums of VOC | Concentration after 28 days [µg/m³] | SERa [µg/(m² · h)] |
|--|-------------------------------------|--------------------|
| VOC without LCI according to AgBB 2021 (sum) | < 5 | < 1.8 |
| VOC without LCI according to eco-INSTITUT-Label (sum) | 3 | 1.1 |
| CMR 2: VOC (incl. VVOC and SVOC) with the following categorisations: Regulation (EC) No. 1272/2008: Category Carc. 2, Muta. 2, Repr. 2; TRGS 905: K2, M2, R2; IARC: Group 2B; DFG (MAK list): Category III3 (sum) | < 1 | < 0.36 |
| Sensitising compounds with the following categorisations: DFG (MAK list): Category IV; Regulation (EC) No. 1272/2008: skin sensitising, respiratory sensitising; TRGS 907 (sum) | < 1 | < 0.36 |
| Bicyclic Terpenes (sum) | < 1 | < 0.36 |
| C9 - C14 Alkanes / Isoalkanes as dekane-equivalent (sum) | < 1 | < 0.36 |
| C4 - C11 Aldehydes, acyclic, aliphatic (sum) | < 2 | < 0.71 |
| C9 - C15 Alkylated benzenes (sum) | < 1 | < 0.36 |
| Cresols (sum) | < 1 | < 0.36 |

| Risk value for assessment of LCI | R-value |
|---|---------|
| R-value according to eco-INSTITUT-Label | 0.13 |
| R-value according to AgBB 2021 | 0.12 |
| R-value according to Belgian regulation | 0.12 |
| R-value according to EU-LCI | 0.12 |

Note:

Due to different requirements in the respective guidelines, the calculation of TVOC, TVVOC, TSVOC and R-value may result in different values. Short-chain carbonyl compounds (C1-C5) are quantified via HPLC acc. to DIN ISO 16000-3:2013-01. Therefore, no toluene equivalents are given for VVOC. These substances are taken into concern by means of their substance specific calibration via the sum of VVOC acc. to DIN EN 16516:2020-10. For VOC however, the substance specific calibration takes place via HPLC whereas the TVOC is calculated using the toluene equivalent determined via Tenax acc. to DIN EN 16516:2020-10.

Cologne, 31/01/2025



Michael Stein, Dipl.-Chem.
(Laboratory Management)

Appendix

Sampling sheet


eco-INSTITUT Germany GmbH
Laborprüfung
Laboratory testing

Probenahmebegleitblatt

*Bitte möglichst alle Felder ausfüllen. Sind die mit einem * gekennzeichneten Felder nicht ausgefüllt, können die Prüfstücke nicht zur Laborprüfung angenommen werden.*

Bitte pro Probe ein Probenahmebegleitblatt ausfüllen! Die Probenahmeanleitung ist unbedingt einzuhalten!

59465-013

| | | | |
|---|--|--|--|
| Auftrag erteilt durch* | KERAKOLL S.P.A. Via dell'artigianato 9 41049 SASSUOLO (MO) | Prüflabor | eco-INSTITUT Germany GmbH Schanzenstr. 6-20, Carlswerk 1.19 D - 51063 Köln Tel. +49 (0)221 - 931245-0 Fax +49 (0)221 - 931245-33 |
| <input type="checkbox"/> Name des Herstellerbetriebes | | Probenahme durch* (Name, Firma, Telefon) | BASTAROLO MARINA +39 0442 424757 |
| <input type="checkbox"/> Name des Vertriebs (wenn abweichend vom Herstellerbetrieb) | | Probenahmeort* | |

| | | | |
|---|---------------|--|-----------------------|
| Prüfstück- / Artikelbezeichnung* | Liquid Paints | Probenart (z.B. Holzwerkstoff, Bodenbelag) | |
| Artikel-Nr. | | Proben- / Chargen-Nr.* | PTKK00176 |
| Modell / Programm / Serie | | Produktionsdatum der Charge* | 5241002032 21.03.2024 |

| | |
|---|---|
| Probe entnommen aus <div style="display: flex; align-items: center;"><input type="checkbox"/> Fertigung <input type="checkbox"/> Lager <input type="checkbox"/> Sonstiges</div> | Datum der Probenahme* 17/07/2024 |
| Lagerort | Lagerung vor der Probenahme <div style="display: flex; align-items: center;"><input type="checkbox"/> offen <input type="checkbox"/> verpackt</div> |
| Verpackungsmaterial | |

ggf. zusätzliche Angaben / Besonderheiten zur Probenahme /
Unklarheiten, Fragen, mögliche negative Einflüsse durch Emissionen am
Probenahmeort - z.B. Kontaminationen während der Produktion/Lagerung

Bestätigung*
Hiermit wird durch die Unterzeichnung (**Probenahme**) die Richtigkeit der oben gemachten Angaben bestätigt.

Datum
(dd/mm/yyyy) 10/09/2024

Unterschrift Bastarolo Marina

eco-INSTITUT Germany GmbH / Schanzenstrasse 6-20 / Carlswerk 1.19 / D-51063 Köln / Germany

Tel. +49 221.931245-0 / Fax +49 221.931245-33 / eco-institut.de / Geschäftsführer: Dr. Frank Kuebart, Daniel Tigges

HRB 17917 / USt-ID: DE 122653300 / Volksbank Rhein-Erft-Köln eG, IBAN: DE60370623651701900010, BIC: GENODE33HAN

List of calibrated Volatile Organic Compounds (VOC)

Aromatic hydrocarbons (31)

Benzene⁴
 1,2,3-Trimethylbenzene
 1,2,4-Trimethylbenzene
 1,3,5-Trimethylbenzene
 1-Isopropyl-2-methylbenzene
 1-Isopropyl-4-methylbenzene
 1,2,4,5-Tetramethylbenzene
 Ethylbenzene
 n-Propylbenzene
 Isopropylbenzene (Cumene)⁴
 1,3-Diisopropylbenzene
 1,4-Diisopropylbenzene
 n-Butylbenzene
 1-Propenylbenzene (beta-Methylstyrene)
 Toluene
 2-Ethyltoluene
 Vinyltoluene
 o-Xylene
 m-/p-Xylene
 Styrene
 Phenylacetylene
 2-Phenylpropene (alpha-Methylstyrene)
 4-Phenylcyclohexene
 1-Phenylcyclohexane
 1-Phenyldecane²
 1-Phenylundecane²
 Indene
 Naphthalene
 1-Methylnaphthalene
 2-Methylnaphthalene
 1,4-Dimethylnaphthalene

Aliphatic hydrocarbons (23)

2-Methylpentane¹
 3-Methylpentane¹
 Methylcyclopentane
 n-Hexane
 Cyclohexane
 Methylcyclohexane
 1,4-Dimethylcyclohexane
 n-Heptane
 2,2,4,6,6-Pentamethylheptane
 n-Octane
 n-Nonane
 n-Decane
 n-Undecane
 n-Dodecane
 n-Tridecane
 n-Tetradecane
 n-Pentadecane
 n-Hexadecane
 Decahydronaphthalene
 1-Octene
 1-Decene
 1-Dodecene
 4-Vinylcyclohexene

Terpenes (12)

delta-3-Carene
 alpha-Pinene
 beta-Pinene
 alpha-Terpinene
 Longipinene
 Limonene
 Longifolene
 Isolongifolene
 beta-Caryophyllene
 alpha-Phellandrene
 Myrcene
 Camphene

Aliphatic alcohols and ether (18)

Ethanol¹
 1-Propanol¹
 2-Propanol¹
 2-Methyl-1-propanol
 1-Butanol
 tert-Butanol
 1-Pentanol
 1-Hexanol
 Cyclohexanol
 2-Ethyl-1-hexanol
 1-Heptanol
 1-Octanol
 1-Nonanol
 1-Decanol
 1,4-Cyclohexandimethanol
 4-Hydroxy-4-methyl-pentan-2-one
 (Diacetone alcohol)
 Methyl-tert-butyl ether (MTBE)¹
 Tetrahydrofuran (THF)

Aromatic alcohols (phenoles) (8)

Furfuryl alcohol
 Benzyl alcohol
 Phenol
 2-Phenylphenol (oPP)
 BHT (2,6-Di-tert-butyl-4-methylphenol)
 o-Cresol
 m-/p-Cresol
 4-Chloro-3-methylphenol (Chlorocresol)

Glycols, Glycol ether, Glycol ester (49)

Ethyleneglycol (Ethan-1,2-diol)
 Propylenglycol (Propane-1,2-diol)
 Diethylene glycol
 Dipropylene glycol
 Neopentyl glycol
 Hexyleneglycol
 Ethyldiglycol
 Ethylene glycol monobutyl ether
 Diethylene glycol methyl ether
 Diethylene glycol monobutyl ether
 Diethylene glycol phenyl ether
 Dipropylene glycol-dimethyl ether

Dipropylene glycol mono-n-butyl ether
 Dipropylene glycol mono-tert-butyl ether
 Dipropylene glycol monomethyl ether
 Dipropylene glycol mono-n-propyl ether
 Tripropylene glycol monomethyl ether
 Triethylene glycol dimethyl ether
 1,2-Propylene glycol dimethyl ether
 1,2-Propylene glycol-n-propyl ether
 1,2-Propylene glycol-n-butyl ether
 Butyl glycolate
 2-Methoxyethanol
 2-Ethoxyethanol
 2-Methylethoxyethanol
 2-Propoxyethanol
 2-Hexoxyethanol
 2-(2-Hexoxyethoxy)ethanol
 2-Phenoxyethanol
 1-Methoxy-2-propanol
 2-Methoxy-1-propanol
 1-Ethoxy-2-propanol
 1-tert-Butoxy-2-propanol
 3-Methoxy-1-butanol
 1,4-Butanediol
 1,2-Dimethoxyethane
 1,2-Diethoxyethane
 1-Methoxy-2-(2-methoxy-ethoxy)ethane
 Ethylene carbonate
 Propylene carbonate
 2-Methoxy-1-propyl acetate
 Diethylene glycol monomethyl ether acetate
 2-Methoxyethyl acetate
 2-Ethoxyethyl acetate
 2-Butoxy ethyl acetate
 Dipropylene glycol monomethyl ether acetate
 Propylene glycol diacetate
 Texanol
 TXIB (Texanol isobutyrate)

Aldehydes (26)

Formaldehyde^{1,3,4}
 Acetaldehyde^{1,3,4}
 Propanal^{1,3}
 Butanal^{1,3}
 3-Methyl-1-butanal
 Pentanal
 Hexanal
 2-Ethylhexanal
 Heptanal
 Octanal
 Nonanal
 Decanal
 Propenal (Acrolein)¹
 Isobutanal (Methacrolein)³
 2-Butenal
 2-Pentenal³
 2-Hexenal
 2-Heptenal
 2-Octenal

2-Nonenal
 2-Decenal
 2-Undecenal
 Ethanedial (Glyoxal)^{1,3}
 Glutaraldehyde
 Furfural
 Benzaldehyde

Ketones (15)

Acetone^{1,3}
 1-Hydroxyacetone
 Ethylmethylketone³
 Methylisobutylketone
 3-Methyl-2-butanone
 Cyclopentanone
 2-Methylcyclopentanone
 Cyclohexanone
 2-Methylcyclohexanone
 2-Hexanone
 2-Heptanone
 Acetophenone
 Isophorone
 Benzophenone⁴
 4-Methylbenzophenone²

Acids (11)

Acetic acid
 Propionic acid
 Pivalic acid
 Butyric acid
 Isobutyric acid
 n-Valeric acid
 n-Caproic acid
 2-Ethylhexanoic acid
 n-Heptanoic acid
 n-Octanoic acid
 Neodecanoic acid

Esters and Lactones (33)

Methyl acetate¹
 Ethyl acetate¹
 Vinyl acetate¹
 Propyl acetate
 Isopropyl acetate
 2-Methoxy-1-methylethyl acetate
 n-Butyl acetate
 Isobutylacetate
 2-Ethylhexyl acetate
 n-Butyl formate

Methyl acrylate
 Methyl methacrylate
 Butyl methacrylate
 Ethyl acrylate
 n-Butyl acrylate
 2-Ethylhexyl acrylate
 2-Ethylhexyl methacrylate
 Hexanediol diacrylate
 Dipropylene glycol diacrylate
 Dimethyl succinate
 Dimethyl glutarate
 Dimethyl adipate
 Dibutyl fumarate
 Dibutyl maleate
 Diisobutyl succinate
 Diisobutyl glutarate
 Butyrolactone
 Dimethyl phthalate
 Diethyl phthalate²
 Dipropyl phthalate²
 Dibutyl phthalate²
 Diisobutyl phthalate²
 (5-Ethyl-1,3-dioxan-5-yl)methyl acrylate

Chlorinated hydrocarbons (18)

Dichloromethane¹
 Trichloromethane (Chloroform)⁴
 Tetrachloromethane
 1,2-Dichloroethane⁴
 1,1,1-Trichloroethane
 2-Chloropropane
 1,2,3-Trichloropropane⁴
 Trichloroethene⁴
 Tetrachloroethene
 trans-1,3-Dichloropropene⁴
 cis-1,3-Dichloropropene⁴
 Chloroprene⁴
 1,3-Dichloro-2-propanol⁴
 Chlorobenzene
 1,4-Dichlorobenzene
 alpha-Chlorotoluene⁴
 alpha,alpha,alpha-Trichlorotoluene⁴
 1,1-Dichloroethene¹

Cyclic siloxanes (5)

Hexamethylcyclotrisiloxane (D3)
 Octamethylcyclotetrasiloxane (D4)
 Decamethylcyclopentasiloxane (D5)
 Dodecamethylcyclohexasiloxane (D6)
 Tetradecamethylcyclheptasiloxane (D7)

Others (42)

1,4-Dioxane⁴
 1,2-Dibromoethane⁴
 2-Nitropropane⁴
 2,3-Dinitrotoluene⁴
 2,4-Dinitrotoluene⁴
 2,6-Dinitrotoluene⁴
 3,4-Dinitrotoluene^{2,4}
 o-Anisidine⁴
 o-Toluidine⁴
 4-Chloro-o-toluidine⁴
 5-Nitro-o-toluidine²
 Acrylonitrile^{1,4}
 2,2'-Azobisisobutyronitrile
 Tetramethylsuccinonitrile
 Azobenzene^{2,4}
 Caprolactam
 Furan^{1,4}
 2-Methylfuran
 2-Pentylfuran
 Methenamine
 Triethylamine
 2-Butanoneoxime⁴
 Triethyl phosphate
 Tributyl phosphate²
 5-Chloro-2-methyl-4-isothiazolin-3-one (CIT)
 2-Methyl-4-isothiazolin-3-one (MIT)
 2-n-Octyl-4-isothiazolin-3-one (OIT)
 Formamide
 Dimethylformamide (DMF)
 Acetamide
 N-Nitrosopyrrolidine⁴
 N-Methyl-2-pyrrolidone
 N-Ethyl-2-pyrrolidone
 N-Butyl-2-pyrrolidone
 Aniline⁵
 4-Chloroaniline⁴
 2-Nitroanisole⁴
 Cyclohexyl isocyanate
 p-Cresidine⁴
 Diethyl sulfate⁴
 Epichlorohydrin⁴
 5-Ethyl-1,3-dioxan-5-methanol

- 1 VVOC
- 2 SVOC
- 3 Analysis acc. to DIN ISO 16000-3:2023-12 (DNPH)
- 4 Carcinogens, category 1A and 1B according to Regulation (EC) No 1272/2008 and TRGS 905
- 5 When analysing with TD-GC-MS, aniline can occur as a thermal decomposition product of other substances (e.g. 1,3-Diphenylguanidine).
 A cold analytical method is recommended to confirm the result.

(Status: August 2024)

Definition of terms

| | |
|---|--|
| CAS No. (Chemical Abstracts Service) | International designation standard for chemical substances |
| CMR | VOCs, VVOCs and SVOCs classified as carcinogenic, mutagenic or toxic for reproduction according to Regulation (EC) No. 1272/2008, TRGS 905, IARC list and DFG (MAK list) |
| Limit of quantification (LOQ) | Lower limit of quantification in the analytical method within the defined measurement uncertainty |
| NIK / LCI | Lowest concentration of interest; substance-specific value for health assessment of emissions from products, indicated in $\mu\text{g}/\text{m}^3$ |
| RT (retention time) | Total time required for an analyte to pass the column (time between injection and detection of the analyte) |
| R value | Sum of quotients of concentration and LCI value for all substances for which a LCI value is derived |
| R value according to AgBB | R-value for all substances $\geq 5 \mu\text{g}/\text{m}^3$ with LCI value, calculated according to the LCI list of the AgBB scheme |
| R-value according to Belgian regulation | R-value for all substances $\geq 5 \mu\text{g}/\text{m}^3$ with LCI-value, calculated according to the LCI-list of the Belgian regulation |
| R value according to eco-INSTITUT-Label | R-value for all substances $\geq 1 \mu\text{g}/\text{m}^3$ with LCI value, calculated according to the LCI list of the AgBB scheme |
| R value according to EU-LCI | R-value for all substances $\geq 5 \mu\text{g}/\text{m}^3$ with EU-LCI value, calculated according to the EU-LCI list of the European Commission |
| SER | Specific emission rate (see "Explanation of Specific Emission Rate SER") |
| SVOC (semi volatile organic compound) | Organic compound eluting in the retention range $> C_{16}$ (n-hexadecane) to C_{22} (docosane) |
| Toluene equivalent | Concentration of a substance quantified by the TIC response factor of toluene (calculation of the concentration by comparing the integral of the substance with the integral of toluene) |
| TSVOC | Sum of the concentrations of all identified and unidentified semi volatile organic compounds eluting in the retention range $> C_{16}$ (n-hexadecane) to C_{22} (docosane) |
| TSVOC according to DIN EN 16516 | Sum of all SVOC $\geq 5 \mu\text{g}/\text{m}^3$ (as toluene equivalent) |
| TSVOC with LCI according to AgBB | Sum of all SVOC with LCI $\geq 5 \mu\text{g}/\text{m}^3$ (quantified substance-specific) |
| TSVOC with LCI according to eco-INSTITUT-Label | Sum of all SVOC with LCI $\geq 1 \mu\text{g}/\text{m}^3$ (quantified substance-specific) |
| TSVOC without LCI according to AgBB | Sum of all SVOC without LCI $\geq 5 \mu\text{g}/\text{m}^3$ (as toluene equivalent) |
| TSVOC without LCI according to eco-INSTITUT label | Sum of all calibrated SVOC without LCI $\geq 1 \mu\text{g}/\text{m}^3$ (quantified substance-specific) and all non-calibrated SVOC without LCI $\geq 1 \mu\text{g}/\text{m}^3$ (as toluene equivalent) |
| TVOC | Sum of the concentrations of all identified and unidentified volatile organic compounds eluting in the retention range from C_6 (n-hexane) to C_{16} (n-hexadecane) |

| | |
|--|--|
| TVOC according to DIN EN 16516 | Sum of all VOC $\geq 5 \mu\text{g}/\text{m}^3$ in the retention range C_6 to C_{16} , calculated as toluene equivalent (used i.a. for M1) |
| TVOC according to AgBB | Sum of all VOCs with LCI $\geq 5 \mu\text{g}/\text{m}^3$ (quantified substance-specific) and all VOCs without LCI $\geq 5 \mu\text{g}/\text{m}^3$ (as toluene equivalent) (used i.a. for the Blue Angel) |
| TVOC according to eco-INSTITUT-Label | Sum of all calibrated VOC $\geq 1 \mu\text{g}/\text{m}^3$ (quantified substance-specific) and all non-calibrated VOC $\geq 1 \mu\text{g}/\text{m}^3$ (as toluene equivalent) (used i.a. for natureplus) |
| TVOC according to ISO 16000-6 | Total area of the chromatogram in the retention range $C_6 - C_{16}$ as toluene equivalent according to DIN ISO 16000-6, Annex A.1 item 3 (used i.a. for CDPH, BIFMA and the French VOC regulation) |
| TVOC without LCI according to AgBB | Sum of all VOCs without LCI $\geq 5 \mu\text{g}/\text{m}^3$ as toluene equivalent |
| TVOC without LCI according to eco-INSTITUT-Label | Sum of all calibrated VOCs without LCI $\geq 1 \mu\text{g}/\text{m}^3$ (quantified substance-specific) and all non-calibrated VOCs without LCI $\geq 1 \mu\text{g}/\text{m}^3$ (as toluene equivalent) |
| TVVOC | Sum of the concentrations of all identified and unidentified very volatile organic compounds eluting in the retention range $< C_6$ (n-hexane) |
| TVVOC according to AgBB | Sum of all VVOC with LCI $\geq 5 \mu\text{g}/\text{m}^3$ (quantified substance-specific) and all VVOC without LCI $\geq 5 \mu\text{g}/\text{m}^3$ (as toluene equivalent) |
| TVVOC according to eco-INSTITUT-Label | Sum of all calibrated VVOC $\geq 1 \mu\text{g}/\text{m}^3$ (substance-specific quantified) and all non-calibrated VVOC $\geq 1 \mu\text{g}/\text{m}^3$ (as toluene equivalent) |
| VOC (volatile organic compound) | Organic compound eluting in the retention range from C_6 (n-hexane) to C_{16} (n-hexadecane) |
| VVOC (very volatile organic compound) | Organic compound eluting in the retention range $< C_6$ (n-hexane) |

Commentary on emission analysis

Test method

Measurement of the volatile organic compounds takes place in the test chamber in conditions similar to those applying in practice. Standardised test conditions are defined for the test chamber regarding loading, air exchange, relative humidity, temperature, and incoming air, based on the type of test specimen and the required guideline. These conditions and the underlying standards are to be found in the section on test methods in the laboratory report.

Air samples are taken from the test chamber at defined points in time during the continuously running test. To this end, approximately 5 L of air are collected from the test chamber at an air flow rate of 100 mL/min on Tenax and approx. 100 L at an air flow rate of 0.8 L/min on silica gel coated with DNPH (2,4-dinitrophenylhydrazine).

After thermal desorption, the substances adsorbed on Tenax are analysed using gas chromatographic separation and mass spectrometric determination. The gas chromatographic separation is performed with a slightly polar capillary column of 60 m in length.

The substances derivatised with DNPH for the determination of formaldehyde and other short-chain carbonyl compounds ($C_1 - C_6$) are analysed using high-performance liquid chromatography (HPLC).

Over 200 compounds, including volatile organic compounds ($C_6 - C_{16}$), semi-volatile organic compounds ($C_{16} - C_{22}$) and – insofar as possible with this method – also very volatile organic compounds (less than C_6) are determined and quantified individually.

All other substances – insofar as possible – are identified through comparison with a library of spectra. The quantification of these substances and non-identified substances is performed through a comparison of their signal area with the signal of toluene.

The determined substance concentrations are corrected using the recovery rate of the internal standard (toluene-d8). Identification and quantification of substances is carried out from a concentration (limit of quantification) of 1 µg per m³ test chamber air or 2 µg/m³ for DNPH-derivatised substances. In the case of highly loaded samples, the evaluation limit of non-calibrated substances is raised in some cases, as it is no longer possible to assign individual, small signals due to the large number of signals.

Quality assurance

The eco-INSTITUT Germany GmbH is granted flexible scope of accreditation pursuant to DIN EN ISO/IEC 17025:2018-03. The accreditation covers the analytical determination of all volatile organic compounds, including the test chamber method.

In each analysis the analytical system is checked using an external standard based on the specifications in standard DIN EN 16516:2020-10. The stability of the analytical systems is documented based on the test standard using control charts.

Laboratory performance is assessed at least once a year in inter-laboratory comparisons by comparing the results with those obtained by other laboratories for identical samples.

A blank is run prior to introducing the test specimen into the test chamber to check for the possible presence of volatile organic compounds.

The expanded measurement uncertainty U for the analytical determination of all volatile organic compounds, including the test chamber method, is estimated to 41.7 %. The calculation is based on DIN ISO 11352:2013-03 (Nordtest).

Explanation of Specific Emission Rate SER

Emission measurements are accomplished in test chambers under defined physical conditions (temperature, relative humidity, room loading, air change rate etc.).

Test chamber measurement results are directly comparable only if the investigations were accomplished under the same basic conditions.

If the differences of the physical conditions refer only to the change of air rate and/or the loading, the "SER" or "specific emission rate" can be used for comparability of the measurement results. The SER indicates how many volatile organic compounds (VOC) are released by the sample for each material unit and hour (h).

The SER can be calculated using the formula below for each proven individual component of the VOC from the data in the test report.

As material units the following are applicable:

| | |
|-----------------------------------|---|
| l = unit of length (m) | relation between emission and length |
| a = unit area (m ²) | relation between emission and surface |
| v = unit volume (m ³) | relation between emission and volume |
| u = piece unit (unit = piece) | relation between emission and complete unit |

From this the different dimensions for SER result:

| | | |
|------------------|------------------|---------------------------|
| length-specific | SER _l | in µg/(m·h) |
| surface-specific | SER _a | in µg/(m ² ·h) |
| volume-specific | SER _v | in µg/(m ³ ·h) |
| unit-specific | SER _u | in µg/(u·h) |

SER thus represents a product specific rate, which describes the mass of the volatile organic compound, which is emitted by the product per time unit at a certain time after beginning of the examination.

$$\text{SER} = q \cdot c$$

- q specific air flow rate (quotient from change of air rate and loading)
c concentration of the measured substance(s)

The result can be indicated in milligrams (mg) in place of micro grams (µg), whereby 1 mg = 1000 µg.